



Doping lanthanum manganites particles with strontium-calcium for application in hyperthermia

L. Rivera Rios^a • I. Perez^b • J. T. Elizalde-Galindo^a • R. Farias^a • P. G. Mani-Gonzalez^{a*}

^aInstituto de Ingeniería y Tecnología, Departamento de Física y Matemáticas, Universidad Autónoma de Ciudad Juárez, Ave. Del Charro 450, Cd. Juárez C.P. 32310, Chihuahua, México

^bCONACYT-Department of Physics and Mathematics, Institute of Engineering and Technology, Universidad Autónoma de Ciudad Juárez

Received 01 20 2021; accepted 08 23 2021

Available 06 30 2022

Abstract: The use of materials capable of controlling the threshold temperature required in hyperthermia, as well as meeting desired requirements in biomedical applications is still a challenge. In the present study, strontium doped calcium lanthanum manganites $\text{La}_{0.7}\text{Ca}_{0.3-x}\text{Sr}_x\text{MnO}_3$ ($x=0, 0.1, 0.15$ and 0.2) were synthesized by co-precipitation method. Vibrating sample magnetometry (VSM) was used to study the effect of Ca-Sr ratio change on magnetic properties. The Curie temperature (T_c) increases from 272 to 315 K as the concentration increases from $x=0$ to $x=0.2$, respectively. Hence the strontium amount plays an essential role in achieving the desired T_c . X-ray diffraction (XRD) was used to identify the rhombohedral structure and scanning electronic microscopy (SEM) was used to characterize the cubic morphology and determinate the average particles size around 800 nm.

Keywords: Hyperthermia; biomedical application; lanthanum manganite doped; Curie temperature; magnetic properties; structure

*Corresponding author.

E-mail address: pierre.mani@uacj.mx (P. G. Mani-Gonzalez).

Peer Review under the responsibility of Universidad Nacional Autónoma de México.

1. Introduction

Current established cancer treatments that exist, such as chemotherapy and radiotherapy, still have considerable side effects. The mitigation of these effects demands new adjuvant therapies that mitigate the consequences of traditional therapies. Differences between healthy and tumor cell behavior under temperature have been the basis for the treatment of tumors by hyperthermia; generally, healthy cells show better resistance to heat than the tumor ones (Wust et al., 2002). Because of this, it is imperative to engineer new compounds and composite materials to control unique thermal, chemical, and electric properties. One of the most promising directions of magnetic particles investigations is the opportunity to use them in engineering, medicine, and biology, particularly for the creation of new magnetic recording systems, biological fluid purification, drug and gene delivery, and hyperthermia (Bubnovskaya et al., 2014; Kalita et al., 2015; Laurent et al., 2008; Vatta et al., 2006). Magnetic hyperthermia is a medical treatment that consists in injecting magnetic particles into cancerous tissue which are in turn heated under the influence of external alternating magnetic fields (Mehdaoui et al., 2010). Also, they have to demonstrate high heating efficiency under an alternating magnetic field to be able to heat the cancerous area with temperatures ranging from 42°C to 45°C (optimal for destroying the tumors) (Solopan et al., 2011).

Magnetite particles (Fe_3O_4) with spinel structure have already found some practical application in medicine (Thiesen & Jordan, 2008). However, Mössbauer effect investigations show that Fe_3O_4 nanoparticles are non-stable: Fe^{2+} partially oxidizes to Fe^{3+} , and this leads to the creation of maghemite ($\gamma\text{-Fe}_2\text{O}_3$) phase. Also, it has the characteristic that the transition temperature from magnetically ordered to paramagnetic state (Curie temperature) is relatively high: $T_c = 585^\circ\text{C}$ (Nikiforov et al., 2013). Since magnetic-field-induced heating is only operative in a magnetically ordered state, high Curie temperature may give rise to uncontrolled and non-uniform heating of tumors to high temperatures, which, in turn, may lead to destroying healthy tissues. These problems can be solved using new materials with tunable Curie temperature by different chemical concentrations on atoms that force magnetic effects (one of them could be Sr as reorder magnetic domains) in the required range of temperature (Shlapa et al., 2016).

Recently, manganese oxides perovskites with general chemical formula $\text{R}_{1-x}\text{A}_x\text{MnO}_3$ (where $\text{R}^{3+} = \text{La}$ and $\text{A}^{2+} = \text{Ca}, \text{Sr}$) have been considered as promising materials capable of meeting these requirements. Curie temperature depends on the chemical composition and can be adjusted by partial La substitution by Sr and Ca according to needs. Lanthanum

manganite doping has been studied as $\text{La}_{0.7}\text{Sr}_{0.3}\text{MnO}_3$ (LSMO) nanoparticles (NPs) stoichiometric in various biomedical applications such as magnetic fluid hyperthermia (MFH), a contrast agent for magnetic resonance, and drug release due to their remarkable thermal and magnetic properties (Epherre et al., 2011; Kačenka et al., 2011; Louguet et al., 2012). The interest in LSMO nanoparticles is mainly due to tuned Curie temperature (by Sr^{2+} doping) between 283 K and 380 K and a large magnetic moment at room temperature. The gradual replacement of Sr by Ca in $\text{La}_{0.75}(\text{Ca}_{0.25-x}\text{Sr}_x)\text{MnO}_3$ decreases in T_c from ~ 340 K for $x=0.25$ to ~ 225 K for $x=0$ (Guo et al., 1998). These nanoparticles have been synthesized by co-precipitation, solid state reaction, microemulsion, thermal decomposition, sol-gel, and hydrothermal synthesis (Jadhav et al., 2013; Thorat et al., 2012).

In the present work, we used the co-precipitation method to synthesize calcium lanthanum manganite with strontium as a dopant. From the study of the structure and magnetic properties of $\text{La}_{0.7}\text{Ca}_{0.3-x}\text{Sr}_x\text{MnO}_3$, the influence of cation concentration (Sr, Ca) on the Curie temperature was investigated. It claims tunable control with chemical composition. This study can be useful for applying lanthanum manganite particles doped with strontium and calcium in hyperthermia treatments.

2. Materials and methods

Strontium doped calcium lanthanum manganite particles were synthesized by the co-precipitation method. Appropriate amounts of La_2O_3 , SrCO_3 , CaCO_3 , and MnO_2 were weighted to reach desired stoichiometry, and each compound was dissolved separately in 25 ml of a hydrochloric acid aqueous solution for about 30 min. In all precursor solutions, were used a molar relationship of 6:1 between salt-acid or oxide-acid. After that, all solutions were mixed, and the mixture was maintained under magnetic stirring for 2 h at room temperature; after this time, the aqueous solution was evaporated at 70°C . Finally, the manganese particles were dried and calcinated in air at 900°C for 24 h. All samples of $\text{La}_{0.7}\text{Ca}_{0.3-x}\text{Sr}_x\text{MnO}_3$ with nominal composition between $0 \leq x \leq 0.2$ were obtained by changing the precursor amount stoichiometrically.

Crystallographic phase indexing was obtained by using a PANalytical X'pert PRO powder X-ray diffractometer (Cu K α radiation, $\lambda = 1.5406 \text{ \AA}$) at 35 kV and 25 mA. The magnetic measurements were carried out employing a vibrating sample magnetometer (VSM) Versalab in the temperature range from 50-350 K. Magnetization curves were analyzed to obtain the Curie temperature, T_c , for different compositions. Particle size and morphology were determined by scanning electron microscopy (SEM) using a HITACHI SU 5000 at 20 kV.

3. Results and discussion

3.1. Structural properties

XRD patterns for $\text{La}_{0.7}\text{Ca}_{0.3-x}\text{Sr}_x\text{MnO}_3$ powders with $0 \leq x \leq 0.2$ compositions are shown in figure 1. According to X-ray patterns, all compositions annealed at 900 °C do not present secondary phases. X'pert High Score Plus software was used to analyze the XRD patterns. For sample $\text{La}_{0.7}\text{Ca}_{0.3}\text{MnO}_3$ the diffraction peaks were compared with standard pattern PDF 01-089-8084 and indexed on the basis of an orthorhombic phase with spatial group $Pnma$.

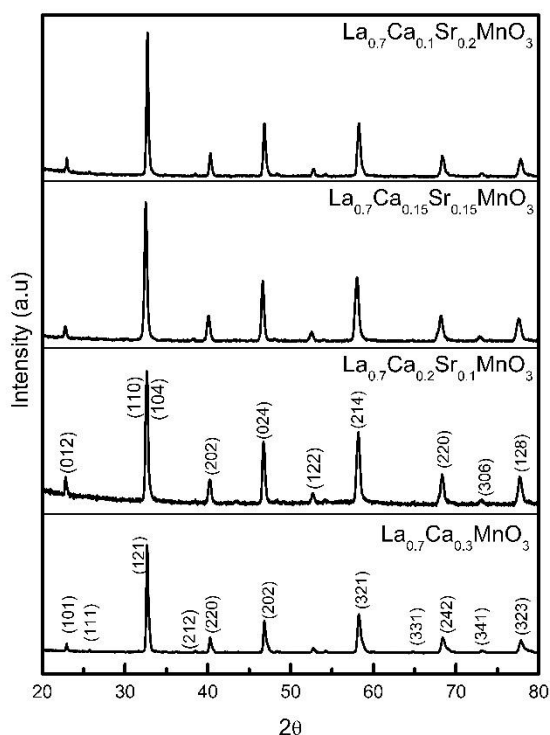


Figure 1. XRD patterns for $\text{La}_{0.7}\text{Ca}_{0.3-x}\text{Sr}_x\text{MnO}_3$ samples. The patterns were indexed according to orthorhombic structure for $\text{La}_{0.7}\text{Ca}_{0.3}\text{MnO}_3$ and rhombohedral structure for $\text{La}_{0.7}\text{Ca}_{0.3-x}\text{Sr}_x\text{MnO}_3$, respectively.

$\text{La}_{0.7}\text{Ca}_{0.3-x}\text{Sr}_x\text{MnO}_3$ samples with $x=0.1, 0.15$ and 0.2 doped with strontium also present a single phase. The diffraction peaks were indexed to the standard pattern PDF 01-089-5612, corresponding to rhombohedral phase with spatial group $R-3c$. All indexed peaks correspond accurately to the crystallographic file used.

3.2. Microstructure analysis

Figure 2 shows the morphology and particle size of the samples observed with a scanning electron microscope (SEM).

It is interesting to note that all samples calcinated at 900 °C for 24 h show cube-shaped particles, which could be associated with the preparation method since wet chemical methods favor this geometry (Spooren et al., 2005). This morphology is similar to that reported by Spooren et al. 2005, which was obtained by hydrothermal synthesis in $\text{La}_{0.5}\text{M}_{0.5}\text{MnO}_3$ ($M=\text{Ca}, \text{Sr}, \text{Ba}$) compounds. We observed a similar morphology in strontium doped calcium lanthanum manganites.

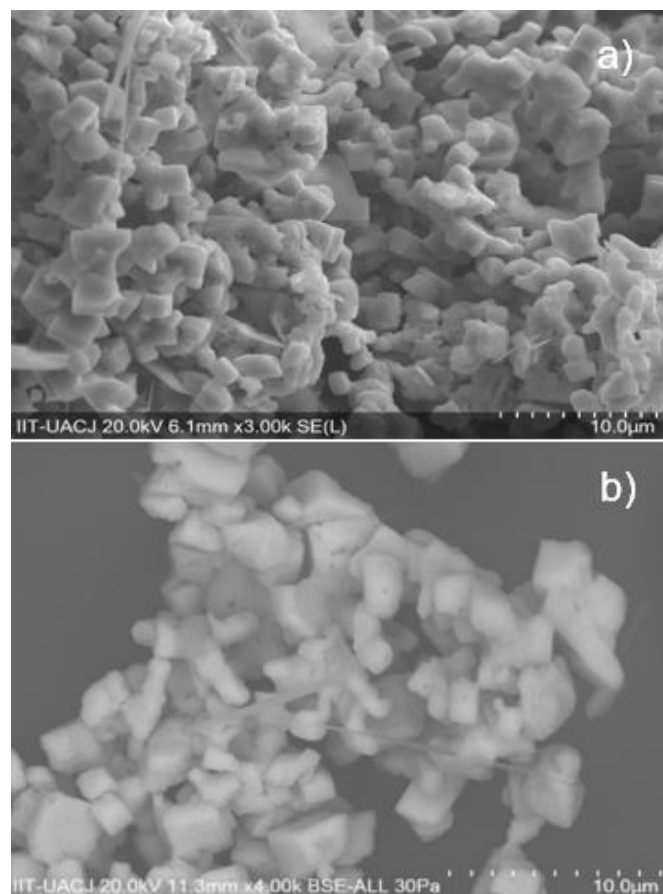


Figure 2. Micrographs of $\text{La}_{0.7}\text{Ca}_{0.3-x}\text{Sr}_x\text{MnO}_3$ particles. a) $\text{La}_{0.7}\text{Ca}_{0.1}\text{Sr}_{0.2}\text{MnO}_3$, b) $\text{La}_{0.7}\text{Ca}_{0.2}\text{Sr}_{0.1}\text{MnO}_3$, c) $\text{La}_{0.7}\text{Ca}_{0.3}\text{MnO}_3$.

A decrement in particle size with increasing Sr content was observed. It seems that incorporation of Sr into the Ca sites enhances particle size reduction, since the particle size decreases from 3 μm for $x=0$ to 1.5 μm for $x=0.2$. Particle size decrement helps for chemical and physical interaction during oncoming particles to cancerous area on hyperthermia applications.

3.3. Magnetic properties

Figure 3 shows the temperature magnetization dependence in Field Cooling (FC) curves for strontium-calcium doped lanthanum manganites samples with different Ca-Sr ratio. These measurements were used to obtain the T_c from magnetization and its temperature derivative (dM/dT). This

relation suggests a dependence with the stoichiometric values. It can be observed in figure 3 according to slope changes. The FC curves show a slight reduction in magnetization as Sr content increase, this behavior is opposite to $\text{La}_{0.7}\text{Sr}_{0.3}\text{MnO}_3$ compounds with calcium substitution obtained by Salili et al. (2015) whose magnetization is higher than in the case of undoped lanthanum manganite. However, we observe a slightly smaller magnetization value in $x=0.10$ (blue line) with respect to $x=0.15$ (pink line). The above is due to different amounts used in magnetic measurements.

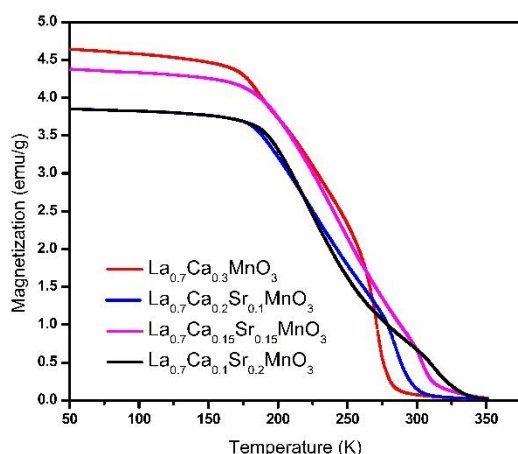


Figure 3. Temperature versus magnetization dependence for samples from $x=0$ to $x=0.2$ as composition in $\text{La}_{0.7}\text{Ca}_{0.3-x}\text{Sr}_x\text{MnO}_3$ (100 Oe field applied).

Figure 4 shows T_c as a function of Sr content. As we can observe, T_c raises from 272 K for $x=0$ to 315 K for $x=0.20$. These results favor Sr as a good candidate for self-controlled (tunable) hyperthermia applications.

The rising of T_c is associated with the increment of Sr^{2+} content since a change in ionic radius takes place. As Sr decrease, the average ionic radius site for the A-site $\langle r_A \rangle$ diminishes, therefore the Mn-O bond distance and Mn-O-Mn bond angle of the perovskite structure. This change causes a weakening in double magnetic exchange interaction between ions Mn^{3+} and Mn^{4+} , formed by Ca and Sr doping, bringing along an increase in T_c (Venkatesh et al., 2012).

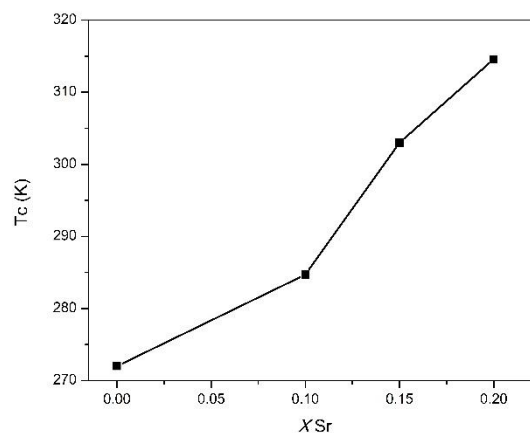


Figure 4. Curie temperature as function of Sr content.

4. Conclusions

In summary, we obtained $\text{La}_{0.7}\text{Ca}_{0.3-x}\text{Sr}_x\text{MnO}_3$ series compounds from $x=0$ to $x=0.2$ composition by co-precipitation method to study the effect of Ca:Sr ratio on Curie temperature. This study has demonstrated that Sr plays an essential role in controlling T_c , which can be tuned by varying the cation ratio as evidenced by magnetic measurements. The rhombohedral structure was obtained when strontium amount increase. This structure suggests better magnetic properties and it is evidence that strontium enter to $\text{La}_{0.7}\text{Ca}_{0.3-x}\text{Sr}_x\text{MnO}_3$ particles. The SEM microstructure analysis was favored with increasing strontium since we observed a reduction in particle size, representing one more advantage in hyperthermia applications.

Conflict of interest

The author(s) have no conflict of interest to declare.

Acknowledgments

The authors acknowledge the financial support for the SEM maintenance from CONACyT through grant INFR-2019-301724.

Financing

The author (s) received no specific funding for this work.

References

- Bubnovskaya, L., Belous, A., Solopan, S., Kovelskaya, A., Bovkun, L., Podoltsev, A., Kondratenko, I., & Osinsky, S. (2014). Magnetic Fluid Hyperthermia of Rodent Tumors Using Manganese Perovskite Nanoparticles. *Journal of Nanoparticles*, 2014, 278761. <https://doi.org/10.1155/2014/278761>
- Epherre, R., Duguet, E., Mornet, S., Pollert, E., Louguet, S., Lecommandoux, S., Schatz, C., & Goglio, G. (2011). Manganite perovskite nanoparticles for self-controlled magnetic fluid hyperthermia: About the suitability of an aqueous combustion synthesis route. *Journal of Materials Chemistry*, 21(12), 4393. <https://doi.org/10.1039/c0jm03963b>
- Guo, Z. B., Yang, W., Shen, Y. T., & Du, Y. W. (1998). Magnetic entropy change in $\text{La}_{0.75}\text{Ca}_{0.25-x}\text{Sr}_x\text{MnO}_3$ perovskites. *Solid State Communications*, 105(2), 89-92. [https://doi.org/10.1016/S0038-1098\(97\)10064-3](https://doi.org/10.1016/S0038-1098(97)10064-3)
- Jadhav, S. V., Nikam, D. S., Khot, V. M., Thorat, N. D., Phadatare, M. R., Ningthoujam, R. S., Salunkhe, A. B., & Pawar, S. H. (2013). Studies on colloidal stability of PVP-coated LSMO nanoparticles for magnetic fluid hyperthermia. *New Journal of Chemistry*, 37(10), 3121. <https://doi.org/10.1039/c3nj00554b>
- Kačenka, M., Kaman, O., Kotek, J., Falteisek, L., Černý, J., Jiráček, D., Herynek, V., Zacharovová, K., Berková, Z., Jendelová, P., Kupčík, J., Pollert, E., Veverka, P., & Lukeš, I. (2011). Dual imaging probes for magnetic resonance imaging and fluorescence microscopy based on perovskite manganite nanoparticles. *Journal of materials chemistry*, 21(1), 157-164. <https://doi.org/10.1039/C0JM01258K>
- Kalita, V. M., Tovstolytkin, A. I., Ryabchenko, S. M., Yelenich, O. V., Solopan, S. O., & Belous, A. G. (2015). Mechanisms of AC losses in magnetic fluids based on substituted manganites. *Physical Chemistry Chemical Physics*, 17(27), 18087-18097. <https://doi.org/10.1039/C5CP02822A>
- Laurent, S., Forge, D., Port, M., Roch, A., Robic, C., Vander Elst, L., & Muller, R. N. (2008). Magnetic Iron Oxide Nanoparticles: Synthesis, Stabilization, Vectorization, Physicochemical Characterizations, and Biological Applications. *Chemical Reviews*, 108(6), 2064-2110. <https://doi.org/10.1021/cr068445e>
- Louguet, S., Rousseau, B., Epherre, R., Guidolin, N., Goglio, G., Mornet, S., Duguet, E., Lecommandoux, S., & Schatz, C. (2012). Thermoresponsive polymer brush-functionalized magnetic manganite nanoparticles for remotely triggered drug release. *Polymer Chemistry*, 3(6), 1408. <https://doi.org/10.1039/c2py20089a>
- Mehdaoui, B., Meffre, A., Lacroix, L.-M., Carrey, J., Lachaize, S., Gougeon, M., Respaud, M., & Chaudret, B. (2010). Large specific absorption rates in the magnetic hyperthermia properties of metallic iron nanocubes. *Journal of Magnetism and Magnetic Materials*, 322(19), L49-L52. <https://doi.org/10.1016/j.jmmm.2010.05.012>
- Nikiforov, V. N., Koksharov, Yu. A., Polyakov, S. N., Malakho, A. P., Volkov, A. V., Moskvina, M. A., Khomutov, G. B., & Irkhin, V. Yu. (2013). Magnetism and Verwey transition in magnetite nanoparticles in thin polymer film. *Journal of Alloys and Compounds*, 569, 58-61. <https://doi.org/10.1016/j.jallcom.2013.02.059>
- Salili, S. M., Ataie, A., Barati, M. R., & Sadighi, Z. (2015). Characterization of mechano-thermally synthesized Curie temperature-adjusted $\text{La}_{0.8}\text{Sr}_{0.2}\text{MnO}_3$ nanoparticles coated with (3-aminopropyl) triethoxysilane. *Materials Characterization*, 106, 78-85. <https://doi.org/10.1016/j.matchar.2015.05.025>
- Shlapa, Y., Kulyk, M., Kalita, V., Polek, T., Tovstolytkin, A., Greneche, J.-M., Solopan, S., & Belous, A. (2016). Iron-Doped (La,Sr)MnO₃ Manganites as Promising Mediators of Self-Controlled Magnetic Nanohyperthermia. *Nanoscale Research Letters*, 11(1), 24. <https://doi.org/10.1186/s11671-015-1223-6>
- Solopan, S., Belous, A., Yelenich, A., Bubnovskaya, L., Kovelskaya, A., Podoltsev, A., ... & Osinsky, S. (2011). Nanohyperthermia of Malignant Tumors. I. Lanthanum-Strontium Manganite Magnetic Fluid as Potential Inducer of Tumor Hyperthermia. *Experimental Oncology*, 33(3), 130-135.
- Spooren, J., Walton, R. I., & Millange, F. (2005). A study of the manganites $\text{La}_{0.5}\text{M}_{0.5}\text{MnO}_3$ (M = Ca, Sr, Ba) prepared by hydrothermal synthesis. *Journal of Materials Chemistry*, 15(15), 1542. <https://doi.org/10.1039/b417003b>

Thiesen, B., & Jordan, A. (2008). Clinical applications of magnetic nanoparticles for hyperthermia. *International Journal of Hyperthermia*, 24(6), 467-474.

<https://doi.org/10.1080/02656730802104757>

Thorat, N. D., Shinde, K. P., Pawar, S. H., Barick, K. C., Betty, C. A., & Ningthoujam, R. S. (2012). Polyvinyl alcohol: An efficient fuel for synthesis of superparamagnetic LSMO nanoparticles for biomedical application. *Dalton Transactions*, 41(10), 3060.

<https://doi.org/10.1039/c2dt11835a>

Vatta, L. L., Sanderson, R. D., & Koch, K. R. (2006). Magnetic nanoparticles: Properties and potential applications. *Pure and Applied Chemistry*, 78(9), 1793-1801.

<https://doi.org/10.1351/pac200678091801>

Venkatesh, R., Theil Kuhn, L., Pryds, N., Bahl, C. R. H., & Bohr, J. (2012). Broadening of the magnetic entropy change in $\text{La}_{0.75}\text{Ca}_{0.15}\text{Sr}_{0.10}\text{MnO}_3$. *Materials Chemistry and Physics*, 132(1), 192-195. <https://doi.org/10.1016/j.matchemphys.2011.11.030>

Wust, P., Hildebrandt, B., Sreenivasa, G., Rau, B., Gellermann, J., Riess, H., Felix, R., & Schlag, P. (2002). Hyperthermia in combined treatment of cancer. *The Lancet Oncology*, 3(8), 487-497.

[https://doi.org/10.1016/S1470-2045\(02\)00818-5](https://doi.org/10.1016/S1470-2045(02)00818-5)